

Non-gapped Fermi surfaces, quasiparticles and the anomalous temperature dependence of the near- E_F electronic states in the CMR oxide $\text{La}_{2-2x}\text{Sr}_{1+2x}\text{Mn}_2\text{O}_7$ with $x = 0.36$

S. de Jong,^{1,*} Y. Huang,¹ I. Santoso,¹ F. Massee,¹ R. Follath,²
O. Schwarzkopf,² L. Patthey,³ M. Shi,³ and M. S. Golden^{1,†}

¹*Van der Waals-Zeeman Institute, University of Amsterdam, NL-1018XE Amsterdam, The Netherlands*

²*BESSY GmbH, Albert-Einstein-Strasse 15, 12489 Berlin, Germany*

³*Paul Scherrer Institute, Swiss Light Source, CH-5232 Villigen, Switzerland*

(Dated: February 2, 2008)

After years of research into colossal magnetoresistant (CMR) manganites using bulk techniques, there has been a recent upsurge in experiments directly probing the electronic states at or near the surface of the bilayer CMR materials $\text{La}_{2-2x}\text{Sr}_{1+2x}\text{Mn}_2\text{O}_7$ using angle-resolved photoemission or scanning probe microscopy. Here we report new, temperature dependent, angle resolved photoemission data from single crystals with a doping level of $x = 0.36$. The first important result is that there is no sign of a pseudogap in the charge channel of this material for temperatures below the Curie temperature T_C . The data show unprecedented sharp spectral features, enabling the unambiguous identification of clear, resolution-limited quasiparticle features from the bilayer split $3d_{x^2-y^2}$ -derived Fermi surfaces both at the zone face and zone diagonal k_F locations. The data show that these low temperature Fermi surfaces describe closed shapes in $k_{||}$, centered at the $(\pi/a, \pi/a)$ points in the 2D Brillouin zone, and are not open and arc-like in nature. The second important result concerns the temperature dependence of the electronic states. The spectra display strong incoherent intensity at high binding energies and a very strong temperature dependence, both characteristics reminiscent of polaronic systems. However, the clear and strong quasiparticle peaks at low temperatures are difficult to place within a polaronic scenario. Careful analysis of the temperature dependent changes in the Fermi surface spectra both at the zone face and zone diagonal regions in k -space indicate that the coherent quasiparticle weight disappears for temperatures significantly above T_C , and that the k -dependence of the T-induced changes in the spectra invalidate an interpretation of these data in terms of the superposition of a ‘universal’ metallic spectrum and an insulating spectrum whose relative weight changes with temperature. In this sense, our data are not compatible with a phase separation scenario.

PACS numbers: 74.25.Jb, 75.47.Lx, 79.60.-i

The bilayered, strontium doped manganites ($\text{La}_{2-2x}\text{Sr}_{1+2x}\text{Mn}_2\text{O}_7$) with $x \approx 0.3 - 0.4$ (abbreviated forthwith LSMO) show on cooling an insulator-metal transition associated with the onset of long range ferromagnetic order. This transition occurs at a maximum Curie temperature T_C , of approximately 130 K (for $x = 0.36$)^{1,2} and goes paired with colossal changes in the magnetoresistance (CMR)³, which in turn have been linked to the large number of spin and orbital degrees of freedom accessible to the near-Fermi-level electronic states. Despite years of research, the microscopic origin of the colossal magnetoresistance effect in these systems is still the subject of much debate.

In general, metallic electrical transport requires the existence of a Fermi surface (FS) upon which quasiparticles (QP's) reside. In this context, LSMO is remarkable, as recent ARPES experiments deep in the ferromagnetic, metallic state indicate the existence of two highly differing regimes. Firstly, for $x = 0.40$,⁴ LSMO is reported to possess a discontinuous FS in the form of arcs centered upon the Brillouin zone diagonal (ZD), with a strong pseudogap opening up towards the Brillouin zone face (ZF). In contrast, at an only 2-4% lower doping level of $x = 0.36 - 0.38$,⁵ the published spectra exhibit clear

quasiparticles at the ZF, leaving open the issue as to the situation at the ZD.

A second, equally important issue regards the temperature dependence of the QP's. Seeing as the metallic behaviour in LSMO is symbiotic with the ferromagnetic order, one would expect coherent QP's at the FS of LSMO to disappear at T_C . This appears to be the case at the ZD in crystals with $x = 0.40$.⁴ Therefore, a recent report proposing both that ZF-QP's exist well above T_C for $x = 0.36$ ⁶ and that metallic behaviour is seen in the ARPES spectra up to a T^* of 300K has stimulated much discussion.

The layered managanites play a special role within the CMR family, as they enable exploitation of powerful, direct experimental probes of the electronic states in both real (STM/STS) and reciprocal space (ARPES). Therefore, it is of paramount importance that the two central issues sketched above of whether the FS of LSMO is pseudogapped below T_C , and whether QP's exist above T_C are investigated in detail.

This paper presents a thorough ARPES study of these key issues in LSMO single crystals with $x = 0.36$. Improved sample quality means we are now able to unambiguously show the existence of QP's at the zone face

for both the antibonding and bonding c-axis bilayer split $3d_{x^2-y^2}$ bands and crucially, also for the ZD direction in the same samples, meaning the $3d_{x^2-y^2}$ -derived FS has no pseudogap at low temperatures. Furthermore, careful analysis of the k -dependence of the data recorded at different temperatures provides strong evidence against a scenario of phase separation into microscopic metallic and insulating ‘patches’ above T_C .⁶

Experiments used the UE112-PGMA beamline at BESSY coupled to an SES100 analyzer and the SIS beamline at the Swiss Light Source equipped with an SES2002 analyser and a $50\text{ }\mu\text{m}$ -sized light spot (μ -ARPES). The total experimental energy broadening at 25K was 30 meV at BESSY and 20 meV at the SLS. The momentum resolution was $0.01\text{ }\pi/a$ at the excitation energies used. Single crystals of LSMO were grown in Amsterdam using the optical floating zone technique. The Curie temperature of the samples was determined using SQUID magnetometry to be 131 K. Prior to measurement, the crystals were cleaved at $T < 40\text{ K}$ in a base pressure of 1×10^{-10} mbar. Very sharp, tetragonal low energy electron diffraction patterns were obtained from all the measured cleavage surfaces.

A typical (E, k) -image, taken at cut 1 of Fig. 1a, is shown in Fig. 1b. A ‘U-shaped’ band - in this case the $3d_{x^2-y^2}$ anti-bonding (AB) bilayer-split band - disperses from a band-bottom located at ca. $\approx 450\text{ meV}$ towards the Fermi level, where each branch displays a sharp feature at low energies indicative of the existence of QP’s. In panels (c) and (d) the (E, k) -images and energy distribution curves (EDC’s) from k_F locations on the FS are shown. In the former, it is evident that low energy spectral weight survives all the way from the ZF to the ZD region of k -space.⁷ In panel (d), the QP’s show up as a small, yet clearly discernable peak at E_F , followed by a hump, at least part of which is due to emission from the deeper lying bonding (B) band (see Fig. 2 and Ref. [8]).

If one takes the presence of low energy spectral weight plus a peaked EDC as a working definition of a QP-signal, it is evident from Fig. 1 that the $d_{x^2-y^2}$ bands support QP’s all round the FS. Consequently, for $x = 0.36$, these FS’s are not zone-diagonal ‘Fermi arcs’ and do not support a pseudogap for $T < T_C$. This is quite unlike the situation reported for $x = 0.40$,⁴ thus making pseudogap behavior for this latter doping level not typical for the layered manganites in general.

On a quantitative level, the clear reduction of the QP peak intensity on going from the ZF to the ZD is intriguing.⁹ Future studies will be required to explore whether these data can be taken as evidence of coupling to orbiton or phonon-orbiton degrees of freedom,¹⁰ which would be expected to be maximal near the zone diagonal where the $3d_{z^2-r^2}$ and $3d_{x^2-y^2}$ -derived FSs approach closest to one another.⁸

In the preceding, two criteria were applied to the data to define whether a QP existed or not. Naturally, it is of interest to examine just how well defined these exci-

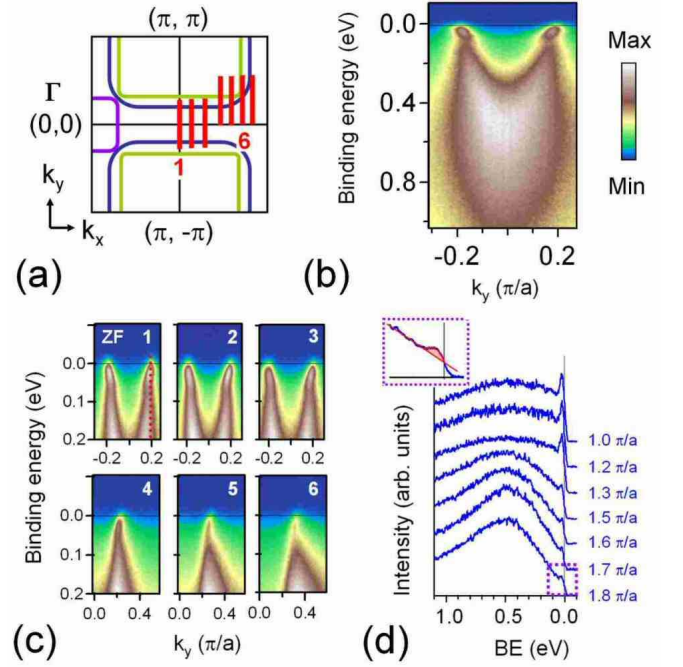


FIG. 1: (a) Schematic of the FS features of LSMO, showing the $3d_{z^2-r^2}$ -based Γ -centered pocket (purple) and the zone corner-centered FS barrels from the $3d_{x^2-y^2}$ -based bonding (green) and anti-bonding (blue) bilayer split bands. The k -space cuts taken are marked in red. (b) (E, k) -image from LSMO with $x = 0.36$ taken at the $(\pi, 0)$ point in k -space [cut 1 in panel (a)]. (c) zoomed images taken at the k -slices shown in panel (a). (d) k_F EDCs from the images shown in (c). The inset (highlighted in purple) shows a zoom of the EDC for $k_x = 1.8\text{ }\pi/a$. The red shading emphasizes that this EDC also supports a small QP peak on top of a sloping background. All data is recorded with $h\nu = 56\text{ eV}$ and $T = 30\text{ K}$.

tations appear to be in both k and E . It is known that effective cleavage surface flatness - over the entirety of the illuminated area - can limit the sharpness of ARPES features. The bilayer manganites do not possess a Van der Waals bonded cleavage plane as the ARPES and STM ‘standard’ oxide $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_8$ does, and therefore measurements on LSMO utilizing a highly focused ‘micro’ excitation spot could deliver better defined QP features.

Figure 2 shows (E, k) -images recorded using the $50\text{ }\mu\text{m}$ light spot at the SLS, together with their corresponding E_F -MDC’s (upper panels) and k_F -EDC’s (lower panels). It is clear from the (E, k) -image in (a) that the qualitative features are very similar to those of Fig. 1b. The big advantage of the ‘ μ -ARPES’ approach can be seen clearly in the top panel of Fig. 2a. Here the E_F MDC’s at $(\pi, 0)$ for the conventional and micro-spot measurements are overlaid. The FWHM of the leading peak of the former is of order $0.06\text{ }\pi/a$, a value equal to the state-of-the-art in the literature (Refs. [4,5]). The small spot data is almost two times narrower, with a FWHM of only $0.035\text{ }\pi/a$. The corresponding k_F EDC shows a more pronounced

peak at E_F , whose width is essentially resolution-limited, as would be expected for a quasiparticle.

Fig. 2b shows the same $(\pi, 0)$ cut for $h\nu = 73$ eV. This photon energy is reported to strongly favour emission from the B band,⁵ and indeed a further U-like feature is seen, with a band bottom located at ca. 800 meV and k_F -wavevectors some $0.1 \pi/a$ greater than those for the AB band. The B band k_F EDC shows a small, narrow peak at E_F signalling the QP, followed by two hump-like features at higher energy.

Consideration of both panel (a) and (b) of Fig. 2, reveals a surprising feature of the μ -ARPES measurements on LSMO in the form of an extra, V-shaped, weak feature indicated in the (E, k) -image of Fig. 2b with a black dotted line. This feature disperses in a parabolic manner around the $(\pi, 0)$ -point (as do the AB and B bands). From an extrapolation, its k_F exceeds $0.5 \pi/a$, a value that is far from matching any FS crossing in band structure calculations.⁸ At present the origin of this feature, which gives rise to the high energy hump in the EDC indicated with an arrow in Fig. 2b, is unknown. Both the simplicity of the observed tetragonal LEED patterns for the cleaved surfaces and the k -space location argue against a simple ‘diffraction replica’ origin.

Fig. 2c shows data taken in the region of the ZD with $h\nu = 56$ eV. Once more a sharp QP peak is seen at E_F , whose intensity, although greater than in the conventional measurement shown in Fig. 1c and d, is still small compared to that seen at the ZF for the same photon energy.

Given the identification of well-defined QP features for both $(\pi, 0)$ centered FSs, one can then move on to examine their nesting characteristics. Fig. 1c shows significant nesting in the ZF region for the AB band (the k_F vectors remain constant over a fair range in k_x). The nesting vector (expressed in units of $2\pi/a$) is simply the k_F value of $q = 0.19$. For the B band at $(\pi, 0)$, the analogous value would be $q = 0.28$, making it a much closer match with q -vectors at which Jahn-Teller correlations above T_C give broad regions of incommensurate x-ray scattering centered at $(\pm\epsilon, 0, \pm 1)$ with $\epsilon = 0.3$.¹¹ This may lie behind the significantly weaker intensity of the QP feature for the B band EDC as compared to the analogous AB band EDC seen in Fig. 2, although one should bear in mind that the polaron correlations seen in x-ray experiments collapse for $T < T_C$.¹¹

To summarize this part of the results, the observation of persistent and resolution-limited QP signals at all k_F locations probed on the $3d_{x^2-y^2}$ -derived FSs using μ -ARPES measurements is not only fully consistent with non-gapped $(\pi, 0)$ -centered FSs in LSMO with $x = 0.36$ at low temperature, but also sets the standard for the sharpest photoemission data on the bilayer manganites recorded to date.

We now turn our attention to the issue of the temperature dependence of the Fermi surface electronic states. Fig. 3 shows data from the $(\pi, 0)$ -point taken at temperatures from 25 K up to 185 K, the latter well above the T_C

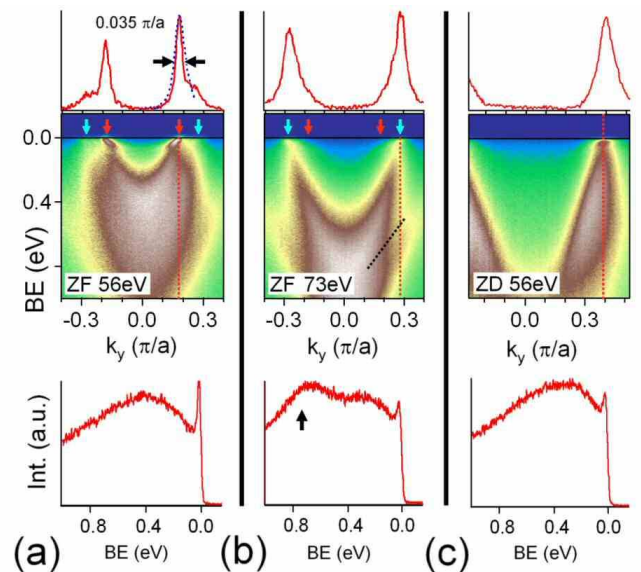


FIG. 2: μ -ARPES data for LSMO with $x = 0.36$ at $T = 30$ K (a) at the zone face with $h\nu = 56$ eV, (b) $h\nu = 73$ eV and (c) near the zone diagonal, $h\nu = 56$ eV. In each case, the upper panels contain E_F MDCs [in panel (a) overlaid with the E_F -MDC from the data shown in Fig. 1b in blue], the central panels the (E, k) -images and lower panels the k_F EDCs. The blue and red arrows mark the k_F -location for the B and AB-bands, respectively.

of 131 K. Panel (a) contains EDMs showing one of the branches of the AB band. It is clear that – apart from thermal broadening – all the EDMs look comparable. It should be noted that the spectral weight of the QP peak does decrease steadily with temperature, as can be seen from the EDCs shown in Fig. 3b. We note here that this decrease in intensity with higher temperatures is larger than the change in thermal broadening can account for on going from 30 to 185 K. Nevertheless, even at 185 K some spectral weight at E_F still remains as a step in the EDC. None of the spectra in Fig. 3 show a gap within the experimental resolution and the accuracy of the energy referencing used. This can be seen from the symmetrized k_F -EDCs displayed in panel (b), although the peak in the 185 K symmetrized spectrum is very small and this EDC might actually be close to being gapped, hinting that a true gap in the charge sector might be opening at even higher temperatures. The fact that spectral intensity at E_F near $(\pi, 0)$ exists even 50 K into the paramagnetic region of the phase diagram⁶ seems at odds with the globally insulating transport characteristic at these elevated temperatures of bilayered LSMO with $x = 0.36$. Therefore, drawing together what our T-dependent data show us up to this point: (i) the QP-peak at lowest energy disappears at or very close to the bulk Curie temperature, yet (ii) at the zone face, there remains (non-peaked) spectral weight at E_F until temperatures of the order of 50 K above T_C .

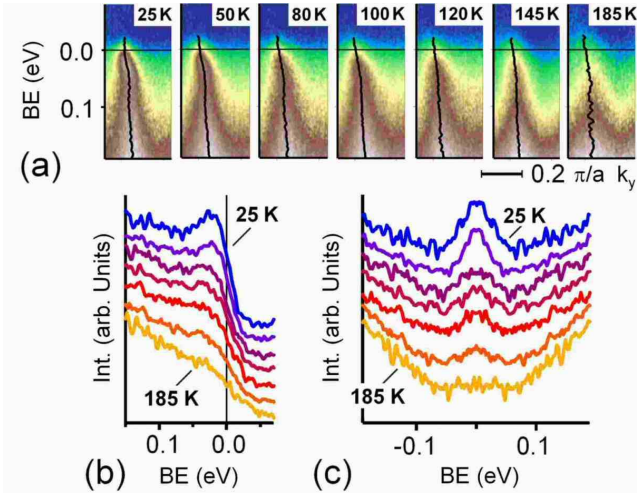


FIG. 3: (a) T-dependence for LSMO $x = 0.36$ at $(\pi, 0)$ ($h\nu=56$ eV, left hand branch). The MDC peak maxima are overlaid using a black solid line. (b) EDCs at k_F for all temperatures, normalized to the intensity at 150 meV BE, and (c) their symmetrized versions (all EDCs are offset vertically).

To further investigate this anomalous temperature dependence, spectra were taken with improved statistics and over a wider binding energy range, both the ZF and ZD regions of the (π, π) -centered Fermi surfaces at low temperature and just below and above T_C . These data are shown in Figure 4. Panel (a) contains the (zoomed) EDMs and (b) the accompanying k_F EDCs.

In panels (c) and (d) of Fig. 4 symmetrized versions are depicted of the EDCs shown in panel (b). Although, as asserted below, the low binding energy coherent spectral weight disappears steadily with increasing temperature at both k -points, the symmetrized spectra show that at the ZF and the ZD again no gap in the charge sector is opening at temperatures up to 140 K.

One striking feature in these T-dependent data, both at the ZF and ZD regions, is that the aforementioned reduction in spectral weight extends over an energy scale of up to 700-800 meV, which is obviously an energy range far in excess of the change in thermal energy. Such large changes have been reported previously for the ZF region in Ref. [6], and their T-dependence has been put forward as an argument for microscopic phase separation, whereby local metallic and insulating regions change their relative abundance steadily with temperature. Vital for this model is that the difference spectra between pairs of k_F EDCs (recorded at different temperatures) can be collapsed onto a single, universal ‘metallic EDC’.⁶ The two difference spectra from our data recorded from the ZF region are shown in Fig. 4e. At first glance, they do look to be scaled versions of one another, but closer inspection reveals that the weight of the QP-peak in the original EDCs decreases much faster between 95 and 145 K than it did between 30 and 145 K, meaning that the difference spectra lose their low energy peak as

temperature increases. As illustrated in the inset of Fig. 4e, this decrease in spectral weight of the QP in the difference spectra persists -though less prominently- if the original EDCs taken at 30 and 95 K are first broadened using an additional Fermi-Dirac distribution (matching the temperature broadening of the spectra recorded at 145 K) before the subtraction takes place. This proves that the decrease in QP spectral weight cannot be attributed to temperature broadening alone. If, for the sake of argument, one were to assign the difference spectra in Fig. 4e to a metallic phase as was done in Ref. [6], the data here show clearly that this ‘metallic’ spectrum loses its coherent QP spectral weight as the temperature climbs above T_C .

An additional, powerful test of this phase separation scenario is given by the k -dependence of the spectral changes with temperature. If temperature essentially only alters the relative percentage of the metallic and insulating patches, then various difference spectra at a FS location other than the ZF should also collapse onto a universal ‘metallic EDC’. From Figs. 1 and 2, it is clear that LSMO with $x = 0.36$ also supports QPs in the zone diagonal region, thus offering the chance of an independent test of the phase separation scenario.

The ZD difference spectra shown in Fig. 4f clearly differ significantly up to binding energies of 300 meV, thus one cannot speak of a universal ‘metallic EDC’ growing monotonically with decreasing temperature for the ZD region of k -space. This, in turn, provides a strong argument against the phase separation model presented in Ref. [6] as being a complete description of the T-dependence of these k -dependent data, as this scenario would demand that the change in spectral weight happens in a similar fashion at both high symmetry points of the Brillouin zone. At this stage, it is interesting to recall that a recent T-dependent STM study of LSMO with $x = 0.30$ ¹² found no signs of a bimodal gap distribution in tunnelling data across more than 2000 different surface locations, which - taken at face value - also argues against phase separation.

Thus, the challenge faced is to reconcile the following four main characteristics of these new, highly-resolved LSMO data for $x = 0.36$:

- i. Existence of clear and sharp QP peaks at all $3d_{x^2-y^2}$ -derived k_F locations probed at low T.
- ii. Strong high BE spectral weight at all temperatures.
- iii. T-dependent changes in the spectra on a scale of up to 800 meV BE.
- iv. Clear differences in the temperature induced effects between the ZF and ZD regions of k -space.

Phase separation as described above would have offered a route to reconcile points (i)-(iii), but cannot account for point (iv). On the other hand, behavior such as described in points (ii)-(iv) has been reported for photoemission from polaronic systems,^{13,14} in which most of

the higher binding energy intensity is due to multiphonon satellites, and a vanishingly weak QP (the ‘zero phonon line’) is left at E_F . The kind of electron-phonon coupling strengths required to generate all the observed high BE incoherent weight¹⁵ seen in these data from LSMO would lead to the complete suppression of the QP feature at E_F , something that evidently does not occur here for $T \ll T_C$ [point (i), above].

From the above, it is apparent that some pieces of the puzzle that are required for a complete and con-

sistent description of the ARPES data from these systems (and their temperature dependence) must still be missing. Despite this pointer towards future work in this area, the data do result in a number of unambiguous and important conclusions. Firstly, that the (π, π) -centered Fermi surfaces of the layered CMR manganite $\text{La}_{1.28}\text{Sr}_{1.72}\text{Mn}_2\text{O}_7$ support quasiparticles, both at the diagonal and the face of the 2D Brillouin zone at low temperatures. This system, therefore, has no pseudogap in the charge sector, thereby excluding the use of the epithet ‘nodal metal’ for this class of materials in general. Secondly, we find that the temperature dependent behavior of both the quasiparticles and of higher lying spectral weight is different at the Brillouin zone face and diagonal. This argues against a model describing the metal-insulator transition as stemming from a percolative growth of metallic clusters in an insulating matrix.

Our thanks to the IFW Dresden group for lending us their spectrometer, and to W. Koops and T. J. Gortenmulder for expert technical support. This work is funded by the FOM (ILP and SICM) and the EU (via I3 contract RII3-CT-2004-506008 at both BESSY and SLS).

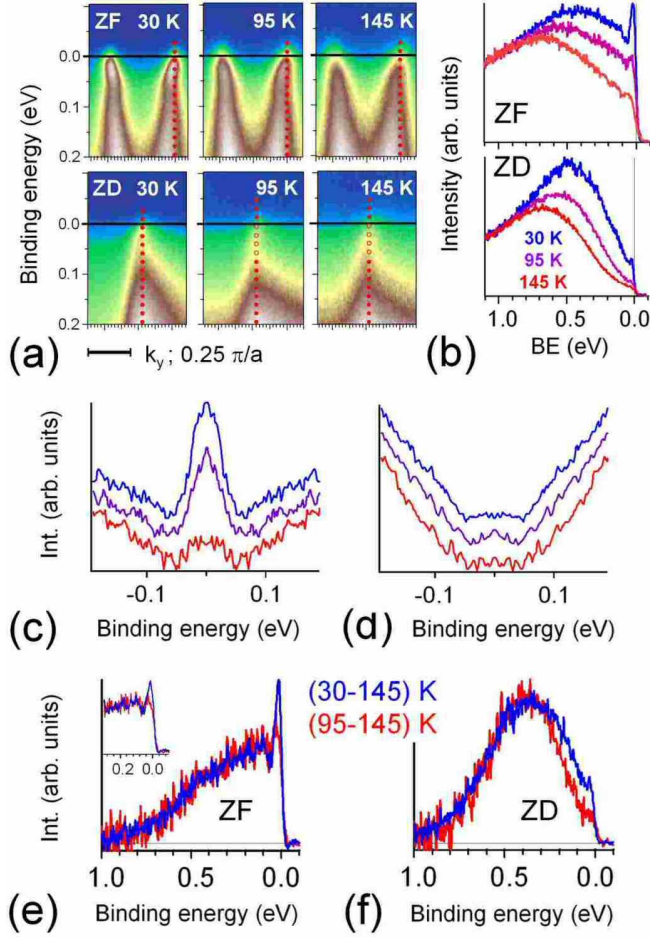


FIG. 4: (a) EDMs of LSMO ($h\nu = 56$ eV, $k_x = 1.0\pi/a$) at the ZF and ZD point in k -space at three different temperatures. (b) EDCs at k_F from the EDMs shown in panel (a) (indicated there with red dotted lines). EDCs are normalized to the high BE intensity, which is equivalent to normalization to the intensity above E_F . (c) Symmetrized EDCs near E_F (scaled at intensity at 200 meV BE) for the three temperatures at the ZF and (d) at the ZD. (e) The scaled difference between the 30 and 95 K EDC (blue curve) and the 95 and 145 K EDC (red curve) for the ZF. The inset shows the same spectra over 300 meV BE for EDCs that are first broadened to match the Fermi-Dirac-distribution at 145 K before subtraction (see text). (f) The scaled difference EDCs of 30 – 145 K EDC (blue curve) and 95 – 145 K EDC (red curve) for the ZD.

-
- * Electronic address: sdejong@science.uva.nl
- † Electronic address: mgolden@science.uva.nl
- ¹ C. D. Ling, J. E. Millburn, J. F. Mitchell, D. N. Argyriou, J. Linton and H. N. Bordallo, Phys. Rev. B **62**, 15096 (2000).
 - ² M. Kubota, H. Fujiokab, K. Ohoyamac, K. Hirotab, Y. Moritomod, H. Yoshizawa and Y. Endohb, J. Phys. Chem. Solids **60**, 1161 (1999).
 - ³ Y. Moritomo, A. Asamitsu, H. Kuwahara and Y. Tokura, Nature (London) **380**, 141 (1996).
 - ⁴ N. Mannella, W. L. Yang, X. J. Zhou, H. Zheng, J. F. Mitchell, J. Zaanen, T. P. Devereaux, N. Nagaosa, Z. Hus-sain and Z.-X. Shen, Nature (London) **438**, 474 (2005).
 - ⁵ Z. Sun, Y.-D. Chuang, A. V. Fedorov, J. F. Douglas, D. Reznik, F. Weber, N. Aliouane, D. N. Argyriou, H. Zheng, J. F. Mitchell, T. Kimura, Y. Tokura, A. Revcolevschi, and D. S. Dessau, Phys. Rev. Lett. **97**, 056401 (2006).
 - ⁶ Z. Sun, J. F. Douglas, A. V. Fedorov, Y.-D. Chuang, H. Zheng, J. F. Mitchell and D. S. Dessau, Nature Physics **3**, 248 (2007).
 - ⁷ For the ZD direction, the bonding and antibonding bilayer split FS's almost touch. Exactly which of these FS's dominates the observed intensity is a moot point.
 - ⁸ X. Y. Huang, O. N. Mryasov, D. L. Novikov, and A. J. Freeman, Phys. Rev. B **62**, 13318 (2000).
 - ⁹ We note here that a reduction of intensity at the ZD in the ARPES experiment could also be (at least partially) the result of: (i) matrix element effects (ii) the fact that the k -space cut at the ZD is not perpendicular to the FS and (iii) the increasing Fermi velocity towards the ZD region of the Brillouin zone.
 - ¹⁰ J. van den Brink, Phys. Rev. Lett. **87**, 217202 (2001).
 - ¹¹ B. J. Campbell, R. Osborn, D. N. Argyriou, L. Vasiliu-Doloc, J. F. Mitchell, S. K. Sinha, U. Ruett, C. D. Ling, Z. Islam and J. W. Lynn, Phys. Rev. B **65**, 014427 (2001).
 - ¹² H. M. Rønnow, Ch. Renner, G. Aeppli, T. Kimura, Y. Tokura, Nature (London) **440**, 1025 (2006).
 - ¹³ C. Kim, F. Ronning, A. Damascelli, D. L. Feng, Z.-X. Shen, B. O. Wells, Y. J. Kim, R. J. Birgeneau, M. A. Kastner, L. L. Miller, H. Eisaki and S. Uchida, Phys. Rev. B **65**, 174516 (2002).
 - ¹⁴ K.M. Shen, F. Ronning, D. H. Lu, W. S. Lee, N. J. C. Ingle, W. Meevasana, F. Baumberger, A. Damascelli, N. P. Armitage, L. L. Miller, Y. Kohsaka, M. Azuma, M. Takano, H. Takagi, and Z.-X. Shen, Phys. Rev. Lett. **93**, 267002 (2004).
 - ¹⁵ We note that the k_F EDCs as presented in this paper also contain spectral weight due to bands located at higher BE, for example the B band and the third, at present unidentified feature mentioned earlier.